

Article

Silver Thin-Film Plated Interconnected Metal Mesh Networks for Virus Detection and Prevention

Tae Min Choi, Hwa Rim Lee  and Sung Gyu Pyo * 

School of Integrative Engineering, Chung-Ang University, 84, Heukseok-ro, Dongjak-gu, Seoul 06974, Republic of Korea; c79411@gmail.com (T.M.C.); ghkfla0725@naver.com (H.R.L.)

* Correspondence: sgpyo@cau.ac.kr

Abstract

Many viruses, bacteria, and pollen that cause diseases such as COVID-19 are inhaled by humans as aerosols. Therefore, wearing a mask to block pathogen-containing aerosols is crucial for disease prevention. However, current masks have a drawback—residual bacteria on the mask surface can become aerosolized again, spreading infections. To address this, a reusable mask incorporating the antibacterial properties of silver particles should be developed to suppress the immune response to pathogens and pollen that contact the mask surface. This study analyzed protein surface changes in pollen shells following electroless silver plating on polypropylene (PP) filters of KF94 masks using microcurrent. Pore density increased from 7.94% before microcurrent application to 14.8% and 16.9%, depending on the duration of exposure. These results suggest that microcurrents alter pollen surfaces and affect the proteins in pollen shells that trigger hay fever, confirming the potential for preventing pollen allergies.

Keywords: reusable masks; disease prevention; pollen allergens; electroless plating; virus inactivation



Academic Editor: Chengyuan Dong

Received: 24 September 2025

Revised: 14 October 2025

Accepted: 16 October 2025

Published: 17 October 2025

Citation: Choi, T.M.; Lee, H.R.; Pyo, S.G. Silver Thin-Film Plated Interconnected Metal Mesh Networks for Virus Detection and Prevention. *Micromachines* **2025**, *16*, 1177. <https://doi.org/10.3390/mi16101177>

Copyright: © 2025 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

The World Health Organization (WHO) declared COVID-19 a global pandemic on 11 March 2020, marking a critical moment in our history. With an estimated more than 776 million cases worldwide by September 2025 (see related links [1]), the disease's high transmissibility continues to disrupt daily life despite decreased mortality due to vaccines. COVID-19 primarily spreads through aerosol droplets [2], and a return to pre-pandemic normalcy remains elusive, underscoring the urgent need for practical solutions.

mRNA COVID-19 vaccines trigger the body to produce antigens and antibodies, inducing both humoral and cell-mediated immunity. They are rapidly produced using genetic mRNA information, unlike traditional vaccines [3], which require the cultivation of pathogens. However, they have the limitation of short-lived immune response [4].

Pollen allergies, which are another threat to human beings, can cause asthma, rhinitis, conjunctivitis, and atopic dermatitis [5–8]. Global warming has increased pollen-producing species, worsening allergic reactions, especially in urbanized areas where pollen combines with combustion particles [6,9]. The most effective prevention for hay fever is the use of disposable masks or antihistamine treatments. However, antihistamines are less favored due to side effects like drowsiness, dizziness, and immunosuppression [10]. As a result, for protection against COVID-19 and pollen allergies, physical blocking methods to prevent virus infections and reduce allergies have become increasingly important.

In 2011, concerns about the effectiveness of general masks against pollen were raised, as bioaerosols containing pollen, fungi, and viruses can cause reinfection [11,12]. HEPA filters can remove over 99.9% of fine dust [13,14], but their glass fiber components are harmful to humans and unsuitable for mask use [15–17]. Therefore, antibacterial treatments are necessary to eliminate bioaerosols on filters, prompting investigations into bacteria removal methods.

Also, Darnell et al. showed that heating SARS-CoV (Severe Acute Respiratory Syndrome Coronavirus) above 65 °C for more than 4 min destroyed its structure [18]. Various sterilization methods are now used on filters, such as heating, ultraviolet (UV) light, and washing with sterilizing liquids [19]. Heating the filter at 70 °C for 5 min can effectively inactivate viruses [20], and studies found that heating melt-blown nonwoven fabric (MNF) in masks at 85 °C for multiple cycles had minimal impact on filtration efficiency [21]. Additionally, UV-C radiation can reduce virus activity by damaging their DNA or RNA [22]. However, UV sterilization requires specialized equipment and the varying penetrating power of different UV wavelengths [23], making it impractical for daily use. Washing masks with sterilizing liquids, such as ethanol, is also effective but reduces the filter's performance [24].

These methods are either inconvenient for daily use or reduce efficiency, leading to research on metallic coatings for masks. Silver, in particular, has shown high antimicrobial efficacy with minimal toxicity to humans [25–30]. Studies have demonstrated that silver-coated filters effectively eliminate bacteria through Ag^+ ion release and surface interaction mechanisms [31,32], and a fiber generating weak microcurrents to suppress bacterial biofilm formation has also been developed [33]. This electroceutical fabric generates weak electric fields and has been found to inactivate viruses transferred from cells. From this perspective, Electroless plating (ELP), also known as auto-catalytic plating, is advantageous for depositing metals on non-conductive and low-conductivity polymers. It is non-destructive to the sample, especially important for delicate or highly sensitive materials. Moreover, the ELP method provides relatively uniform plating on fibrous materials, making it a reliable and convenient option for plating non-metals and polymers such as electrospun nanofibers and PP filters [34–37].

This study assesses the antibacterial properties of silver and explores the development of an electric mask capable of conducting microcurrents for sterilization. Silver thin films were deposited via ELP onto the inner PP filter of a KF94 mask. Additionally, surface structure modification of cottonwood pollen, a major allergen, was performed. The goal is to create an electric mask powered by a button-cell battery that is convenient and easy to use.

2. Materials and Methods

Ag deposition on the KF94 mask and polypropylene (PP) filter was carried out via ELP. The ELP process followed the classical Tollens-type reduction route [38–41].

Prior to plating, the polypropylene (PP) filter was sequentially cleaned with deionized (DI) water and ethanol for 3 min each at room temperature, followed by sensitization and activation to create catalytic sites for electroless deposition. The filter was immersed in a SnCl_2 –HCl solution (0.5625 g SnCl_2 and 1 mL HCl in 250 mL DI water) for 3 min, then activated in a PdCl_2 –HCl solution (0.1875 g PdCl_2 and 1 mL HCl in 250 mL DI water) for an additional 3 min under the same conditions.

Silver deposition was then performed by mixing AgNO_3 , NaOH, glucose, tartaric acid, ethanol, NH_4OH , and DI water. Specifically, 1.75 g of silver nitrate (AgNO_3) was dissolved in 60 mL of DI water to prepare the silver precursor solution. Separately, 0.75 g of sodium hydroxide (NaOH), 2.7 g of glucose, 0.24 g of tartaric acid, and 6 mL of ethanol

were dissolved in 60 mL of DI water to form the alkaline reducing solution. The two solutions were then combined under continuous stirring at 25 °C. Subsequently, 10 mL of ammonium hydroxide (28–30 wt%) was added dropwise until the precipitate completely dissolved with 12 of total solution pH.

The KF94 mask filters were immersed in the resulting electroless plating bath and stirred at 25 °C. After plating, the samples were rinsed with DI water and dried at 70 °C under ambient conditions. Chemical reactions for Ag ELP are drawn in Figure 1.

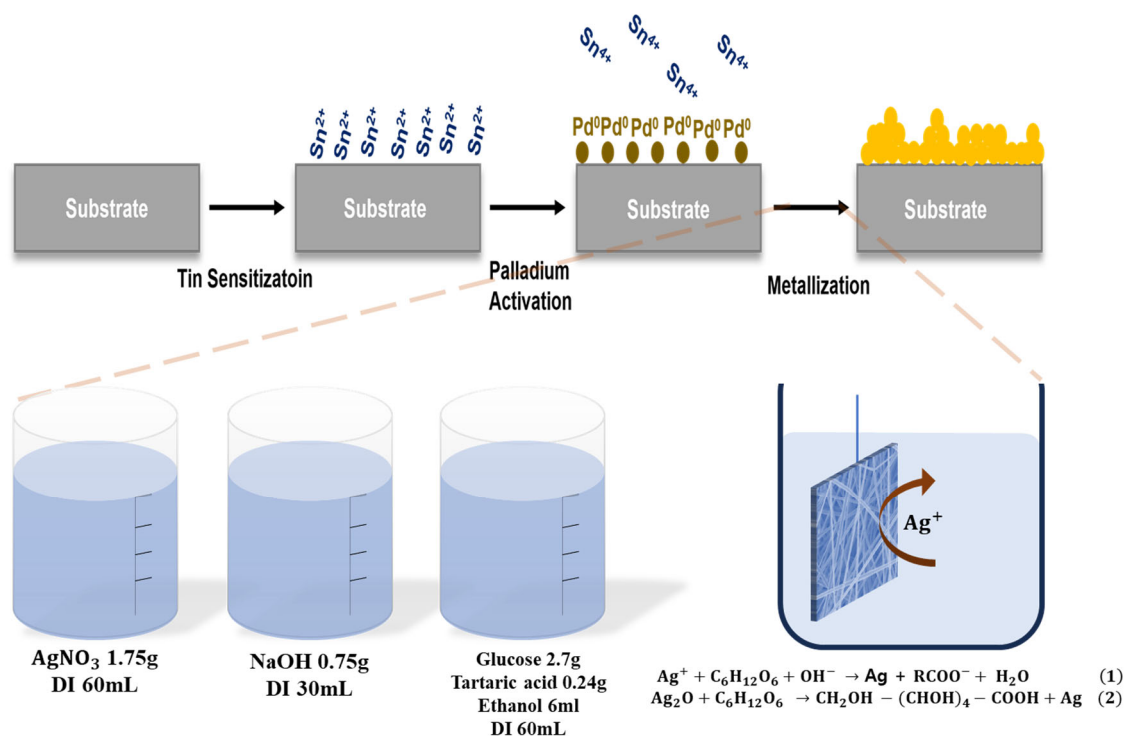


Figure 1. Experimental procedure for the electroless Ag plating process.

The surface characteristics of the plated filter were analyzed using field emission scanning electron microscopy (FE-SEM, SIGMA 300, Carl Zeiss, Oberkochen, Deutschland), and the sheet resistance was measured with a 4-point probe to confirm conductivity.

A direct current power supply was connected to the plated filter, and a current of 1 mA was passed to observe the change caused by the microcurrent. Then, cottonwood pollen (Sigma Aldrich, St. Louis, MO, USA) was placed on the filter for 0–2 s, and the effect of the current on it was observed. Then, the diameter and density of the holes on the surface were calculated using FE-SEM and an image analysis program to evaluate the surface change.

3. Results and Discussion

3.1. PP Filter ELP

Different plating times (ranging from 1 to 5 min) were examined to identify the optimal conditions for achieving the highest conductivity and ensuring successful electroless plating on the PP filter. Figure 2 presents the FE-SEM images of the electroless silver-plated PP filter. Particles were formed on the plated filter after 1 min of the ELP process. After 2 min, silver was deposited in the form of a dense film.

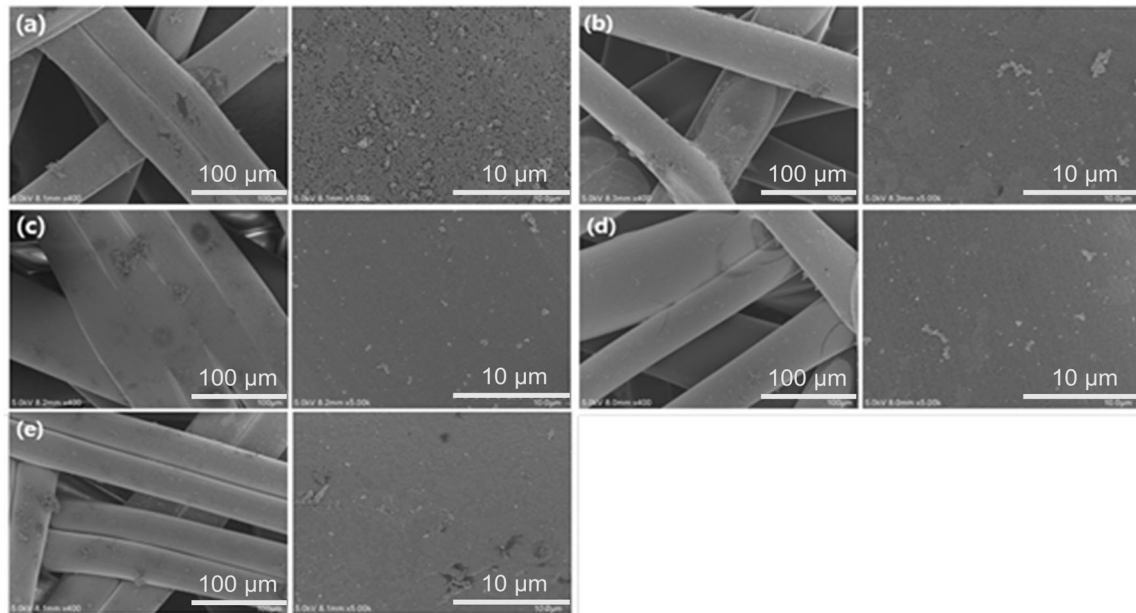


Figure 2. FE-SEM photographs: PP filter with Ag ELP for (a) 1 min, (b) 2 min, (c) 3 min, (d) 4 min, and (e) 5 min.

Figure 3 shows a graph of sheet resistance based on the plating time of the mask filter. The fabricated PP filter + Ag filter had a sheet resistance of $0.6 \Omega/\text{sq}$ after 1 min of electroless plating, which decreased to $0.2 \Omega/\text{sq}$ after 2 min. After 3 min, it decreased to approximately $0.1 \Omega/\text{sq}$ and stayed at a similar value for 5 min. The conductivity was confirmed for hay fever prevention and sterilization by applying current; the sheet resistance decreased as electroless plating progressed. The plating time was increased to further check the change in sheet resistance.

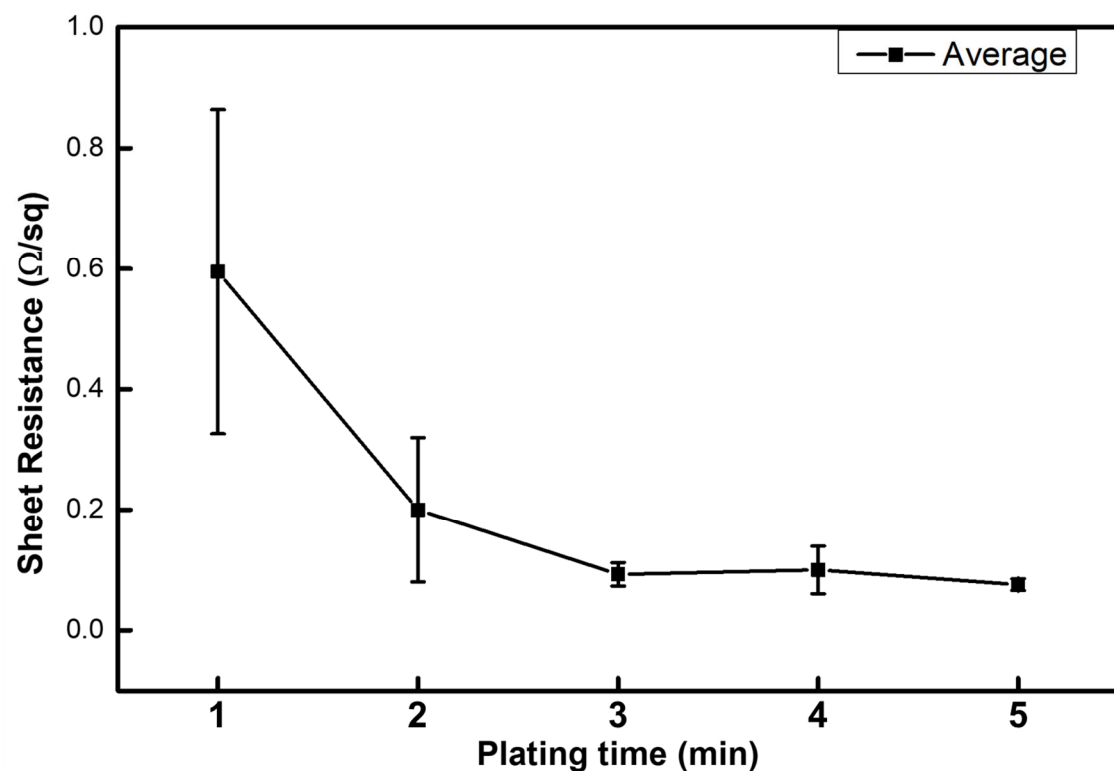


Figure 3. Sheet resistance change in PP + Ag filter according to the Ag electroless plating time.

3.2. Variation in the Pollen Surface

FE-SEM and image analysis software were used to examine the changes in the cottonwood pollen surface following the application of an electric current. Two pollen samples were analyzed for each duration of current application. Figure 4 shows the FE-SEM images of the cottonwood pollen surfaces before and after the current application. The graph in Figure 5 presents the results of the hole diameter change analysis based on the current application time. The diameter of the surface holes increased with the application of current. Specifically, the hole area density in a $4\ \mu\text{m} \times 3\ \mu\text{m}$ area of the pollen sample increased by 86% from before to 1 s after the current application. Consequently, the density of holes in the corresponding area increased from 7.94% before applying the current to 14.8% and 16.9%. The microcurrent-induced modification of pollen morphology may also be associated with conformational changes in surface or shell proteins that are responsible for allergenic reactions. Previous studies have reported that even low-intensity direct electric currents or weak electric fields can induce irreversible structural rearrangements in protein molecules [42,43]. These findings suggest that the weak current applied in this study could similarly affect pollen surface proteins, potentially reducing the antigen–antibody interaction responsible for allergic responses.

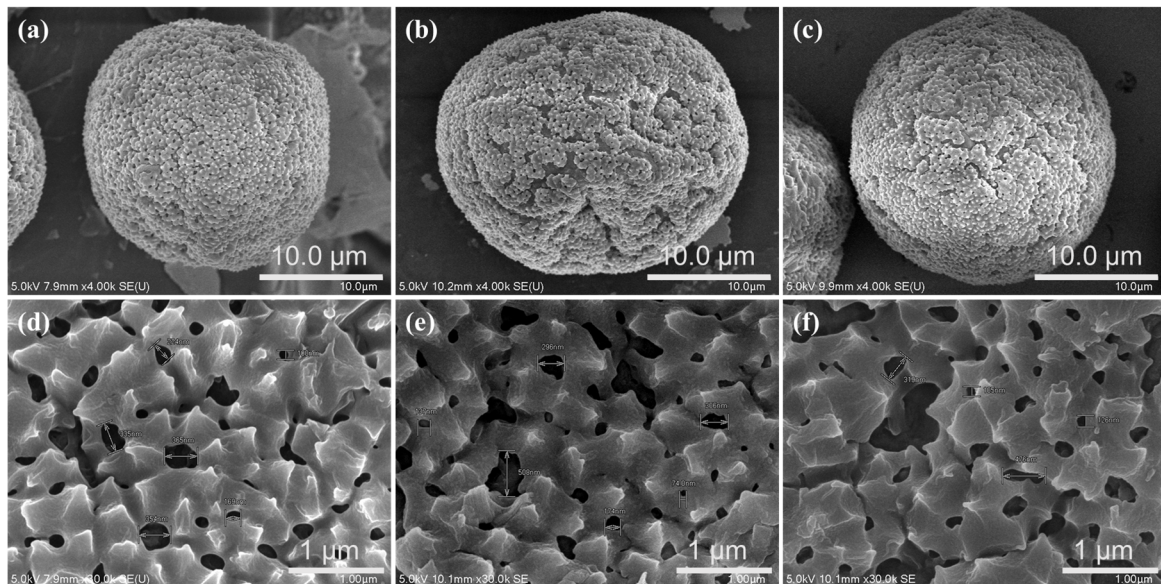


Figure 4. Variation in pollen surface on PP + Ag filter according to current application time: (a,d) before current application, (b,e) 1 s and (c,f) 2 s after application.

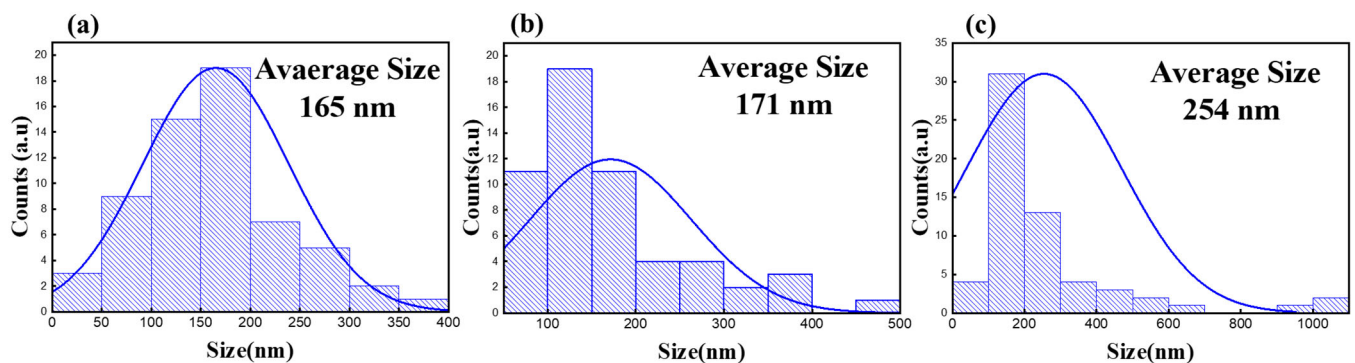


Figure 5. Variation in the hole diameter of the cottonwood pollen surface based on current application time, (a) no current, (b) 1 mA for 1 s, (c) 1 mA for 2 s.

4. Conclusions

In this study, a silver-coated polypropylene (PP) filter for the KF94 mask was successfully fabricated via the electroless silver plating (ELP) method. This process provides a facile and scalable route to impart both electrical conductivity and antimicrobial functionality onto commercial polymer filters without high-temperature or vacuum-based deposition processes, unlike conventional sputtering or CVD methods. The sheet resistance of the silver-plated filter significantly decreased from 0.6 Ω /sq to 0.1 Ω /sq with increasing plating time, demonstrating stable current transport across the fibrous surface.

Furthermore, when a microcurrent of 1 mA was applied to the Ag-coated filter, surface modification of the adhered pollen particles was observed. FE-SEM analysis revealed an increase in pore density on the pollen surface from 7.94% to 14.8% and 16.9%, suggesting that the applied current induced morphological and possibly biochemical alterations of the pollen shell, which contains allergenic proteins. This behavior implies a potential new approach for in situ denaturation or structural modification of airborne allergens through controlled microcurrent exposure.

Compared with previous studies on antibacterial or antiviral filters that primarily rely on passive Ag ion release or photocatalytic reactions, the present ELP-based electrically active filter offers an additional electrochemical pathway for allergen deactivation under low-voltage conditions. This dual-function mechanism distinguishes it from conventional Ag-coated or electrospun functional filters.

Future work will focus on quantifying pollen adsorption and allergen reduction efficiency in simulated breathing environments, as well as evaluating differential pressure and adhesion characteristics to optimize comfort and filtration performance for real mask applications.

Author Contributions: Conceptualization, T.M.C. and S.G.P.; methodology, H.R.L. and S.G.P.; validation, T.M.C. and H.R.L.; writing—original draft preparation, T.M.C.; supervision, S.G.P.; project administration, S.G.P. All authors have read and agreed to the published version of the manuscript.

Funding: This work was supported by the Technology Innovation Program (or Industrial Strategic Technology Development Program-Public-private joint investment semiconductor R&D program (K-CHIPS) to foster high-quality human resources) (“RS-2023-00237003”, High selectivity etching technology using cryoetch) funded by the Ministry of Trade, Industry & Energy (MOTIE, KOREA) (1415187674) And This work was also supported by the Technology Innovation Program (No. 20022472) funded by the Ministry of Trade, Industry and Energy (MOTIE, KOREA).

Data Availability Statement: Dataset available on request from the authors.

Conflicts of Interest: The authors declare no conflicts of interest.

References

1. World Health Organization 2023 data.who.int, WHO Coronavirus (COVID-19) Dashboard > Cases. Available online: <https://data.who.int/dashboards/covid19/cases> (accessed on 15 October 2025).
2. Wang, J.; Du, G. COVID-19 may transmit through aerosol. *Ir. J. Med. Sci.* **2020**, *189*, 1143–1144. [[CrossRef](#)] [[PubMed](#)]
3. Pardi, N.; Hogan, M.J.; Porter, F.W.; Weissman, D. mRNA vaccines—A new era in vaccinology. *Nat. Rev. Drug Discov.* **2018**, *17*, 261–279. [[CrossRef](#)] [[PubMed](#)]
4. Cagigi, A.; Douradinha, B. Have mRNA vaccines sentenced DNA vaccines to death? *Expert Rev. Vaccines* **2023**, *22*, 1154–1167. [[CrossRef](#)] [[PubMed](#)]
5. Brown, H.M.; Irving, K.R. The size and weight of common allergenic pollens. *Allergy* **1973**, *28*, 132–137. [[CrossRef](#)]
6. Taylor, P.E.; Flagan, R.C.; Valenta, R.; Glovsky, M.M. Release of allergens as respirable aerosols: A link between grass pollen and asthma. *J. Allergy Clin. Immunol.* **2002**, *109*, 51–56. [[CrossRef](#)]
7. Corren, J. Allergic rhinitis and asthma: How important is the link? *J. Allergy Clin. Immunol.* **1997**, *99*, S781–S786. [[CrossRef](#)]
8. D’amato, G.; Liccardi, G.; D’amato, M.; Holgate, S. Environmental risk factors and allergic bronchial asthma. *Clin. Exp. Allergy* **2005**, *35*, 1113–1124. [[CrossRef](#)]

9. Cox, C.S. Airborne bacteria and viruses. *Sci. Prog.* **1989**, *73*, 469–499.
10. Hindmarch, I.; Shamsi, Z. Antihistamines: Models to assess sedative properties, assessment of sedation, safety and other side-effects. *Clin. Exp. Allergy* **1999**, *29*, 133–142. [\[CrossRef\]](#)
11. Cheng, K.K.; Lam, T.H.; Leung, C.C. Wearing face masks in the community during the COVID-19 pandemic: Altruism and solidarity. *Lancet* **2022**, *399*, e39–e40. [\[CrossRef\]](#)
12. Pasanen, A.-L.; Keinänen, J.; Kalliokoski, P.; Martikainen, P.I.; Ruuskanen, J. Microbial growth on respirator filters from improper storage. *Scand. J. Work Environ. Health* **1993**, *19*, 421–425. [\[CrossRef\]](#) [\[PubMed\]](#)
13. First, M.W. HEPA filters. *J. Am. Biol. Saf. Assoc.* **1998**, *3*, 33–42. [\[CrossRef\]](#)
14. Agrawal, S.R.; Kim, H.-J.; Lee, Y.W.; Sohn, J.-H.; Lee, J.H.; Kim, Y.-J.; Lee, S.-H.; Hong, C.-S.; Park, J.-W. Effect of an air cleaner with electrostatic filter on the removal of airborne house dust mite allergens. *Yonsei Med. J.* **2010**, *51*, 918–923. [\[CrossRef\]](#) [\[PubMed\]](#)
15. Min, K.D.; Park, W.H.; Youk, J.H.; Kwark, Y.-J. Controlling size and distribution of silver nanoparticles generated in inorganic silica nanofibers using poly(vinyl pyrrolidone). *Macromol. Res.* **2008**, *16*, 626–630. [\[CrossRef\]](#)
16. Isaeva, V.I.; Aizenshtein, é.M.; Soboleva, O.N. World production and use of polypropylene fibres and thread. A review. *Fibre Chem.* **1997**, *29*, 269–281. [\[CrossRef\]](#)
17. Zhukovskii, V.A.; Voronova, I.G.; Khokhlova, V.A.; Gridneva, A.V.; Filipenko, T.S. Technological developments in making polypropylene surgical monofilaments. *Fibre Chem.* **2008**, *40*, 322–329. [\[CrossRef\]](#)
18. Darnell, M.E.; Subbarao, K.; Feinstone, S.M.; Taylor, D.R. Inactivation of the coronavirus that induces severe acute respiratory syndrome, SARS-CoV. *J. Virol. Methods* **2004**, *121*, 85–91. [\[CrossRef\]](#)
19. Pullangott, G.; Kannan, U.; Gayathri, S.; Kiran, D.V.; Maliyekkal, S.M. A comprehensive review on antimicrobial face masks: An emerging weapon in fighting pandemics. *RSC Adv.* **2021**, *11*, 6544–6576. [\[CrossRef\]](#)
20. Liao, L.; Xiao, W.; Zhao, M.; Yu, X.; Wang, H.; Wang, Q.; Chu, S.; Cui, Y. Can N95 Respirators Be Reused after Disinfection? How Many Times? *ACS Nano* **2020**, *14*, 6348–6356. [\[CrossRef\]](#)
21. Shan, X.; Zhang, H.; Liu, C.; Yu, L.; Di, Y.; Zhang, X.; Dong, L.; Gan, Z. Reusable self-sterilization masks based on electrothermal graphene filters. *ACS Appl. Mater. Interfaces* **2020**, *12*, 56579–56586. [\[CrossRef\]](#)
22. Owens, M.U.; Deal, D.R.; Shoemaker, M.O.; Knudson, G.B.; Meszaros, J.E.; Deal, J.L. High-Dose Ultraviolet C Light Inactivates Spores of *Bacillus Atrophaeus* and *Bacillus Anthracis* Sterne on Nonreflective Surfaces. *Appl. Biosaf.* **2005**, *10*, 240–247. [\[CrossRef\]](#)
23. Bentancor, M.; Fernández, S.; Viera, F.; Etcheverry, S.; Poradosú, C.; D’Angelo, P.; Montemuiño, H.; Mirazo, S.; Irigoyen, Á.; Sanabria, A.; et al. LUCIA: An open source device for disinfection of N95 masks using UV-C radiation. *HardwareX* **2021**, *9*, e00181. [\[CrossRef\]](#) [\[PubMed\]](#)
24. Ullah, S.; Ullah, A.; Lee, J.; Jeong, Y.; Hashmi, M.; Zhu, C.; Joo, K.I.; Cha, H.J.; Kim, I.S. Reusability Comparison of Melt-Blown vs Nanofiber Face Mask Filters for Use in the Coronavirus Pandemic. *ACS Appl. Nano Mater.* **2020**, *3*, 7231–7241. [\[CrossRef\]](#) [\[PubMed\]](#)
25. Lansdown, A.B. Silver in health care: Antimicrobial effects and safety in use. *Curr. Probl. Dermatol.* **2006**, *33*, 17–34. [\[CrossRef\]](#)
26. Marambio-Jones, C.; Hoek, E.M. A review of the antibacterial effects of silver nanomaterials and potential implications for human health and the environment. *J. Nanopart. Res.* **2010**, *12*, 1531–1551. [\[CrossRef\]](#)
27. Mijndendonckx, K.; Leys, N.; Mahillon, J.; Silver, S.; Van Houdt, R. Antimicrobial silver: Uses, toxicity and potential for resistance. *Biomaterials* **2013**, *26*, 609–621. [\[CrossRef\]](#)
28. Saeed, N.; Atiq, A.; Rafiq, F.; Khan, I.; Atiq, M.; Saleem, M.; Anjum, D.H.; Usman, Z.; Abbas, M. Engineering of self-assembled silver-peptide colloidal nanohybrids with enhanced biocompatibility and antibacterial activity. *Sci. Rep.* **2024**, *14*, 26398. [\[CrossRef\]](#)
29. Le Ouay, B.; Stellacci, F. Antibacterial activity of silver nanoparticles: A surface science insight. *Nano Today* **2015**, *10*, 339–354. [\[CrossRef\]](#)
30. Sotiriou, G.A.; Pratsinis, S.E. Antibacterial activity of nanosilver ions and particles. *Environ. Sci. Technol.* **2010**, *44*, 5649–5654. [\[CrossRef\]](#)
31. Sun, Z.; Kong, Y.; Lan, L.; Meng, Y.; You, T.; Pauer, R.; Wang, H.; Zhang, Y.; Tang, M.; Demello, A. A High Efficiency, Low Resistance Antibacterial Filter Formed by Dopamine-Mediated In Situ Deposition of Silver onto Glass Fibers. *Small* **2024**, *20*, 2301074. [\[CrossRef\]](#)
32. Tarimala, S.; Kothari, N.; Abidi, N.; Hequet, E.; Fralick, J.; Dai, L.L. New approach to antibacterial treatment of cotton fabric with silver nanoparticle-doped silica using sol-gel process. *J. Appl. Polym. Sci.* **2006**, *101*, 2938–2943. [\[CrossRef\]](#)
33. van der Elst, L.A.; Gokce, M.; Coulter, J.R.; Cavdar, Z.B.; Koraganji, V.N.; Ozturk, M.; Ghatak, S.; Sen, C.K.; Gumennik, A. Microstructured Electroceutical Fiber-Device for Inhibition of Bacterial Proliferation in Wounds. *Adv. Mater. Interfaces* **2023**, *10*, 2201854. [\[CrossRef\]](#)
34. Pinto, N.J.; Carrión, P.; Quiñones, J.X. Electroless deposition of nickel on electrospun fibers of 2-acrylamido-2-methyl-1-propanesulfonic acid doped polyaniline. *Mater. Sci. Eng. A* **2004**, *366*, 1–5. [\[CrossRef\]](#)

35. Drew, C.; Liu, X.; Ziegler, D.; Wang, X.; Bruno, F.F.; Whitten, J.; Samuelson, L.A.; Kumar, J. Metal Oxide-Coated Polymer Nanofibers. *Nano Lett.* **2003**, *3*, 143–147. [[CrossRef](#)]
36. Kim, N.K.; Kim, K.; Jang, H.; An, T.; Shin, H.-J.; Kim, G.H. Microheater with copper nanofiber network via electrospinning and electroless deposition. *Sci. Rep.* **2023**, *13*, 22248. [[CrossRef](#)]
37. Lin, M.-F.; Chang, K.-W.; Lee, C.-H.; Wu, X.-X.; Huang, Y.-C. Electrospun P3HT/PVDF-HFP semiconductive nanofibers for triboelectric nanogenerators. *Sci. Rep.* **2022**, *12*, 14842. [[CrossRef](#)]
38. Montazer, M.; Allahyarzadeh, V. Electroless plating of silver nanoparticles/nanolayer on polyester fabric using AgNO₃/NaOH and ammonia. *Ind. Eng. Chem. Res.* **2013**, *52*, 8436–8444. [[CrossRef](#)]
39. Montazer, M.; Alimohammadi, F.; Shamei, A.; Rahimi, M.K. In situ synthesis of nano silver on cotton using Tollens' reagent. *Carbohydr. Polym.* **2012**, *87*, 1706–1712. [[CrossRef](#)]
40. Tollens, B. Ueber ammon-alkalische Silberlösung als Reagens auf Aldehyd. *Berichte Dtsch. Chem. Ges.* **1882**, *15*, 1635–1639. [[CrossRef](#)]
41. Chen, H.; Liao, F.; Yuan, Z.; Han, X.; Xu, C. Simple and fast fabrication of conductive silver coatings on carbon fabrics via an electroless plating technique. *Mater. Lett.* **2017**, *196*, 205–208. [[CrossRef](#)]
42. Lin, F.; Zhu, X.; Li, X.; Guo, W.; Lu, Y.; Sun, L.; Zhu, G. Low-intensity direct current electric field-induced structural and functional modulation of key denitrifying enzyme: In vitro experimental and molecular dynamics simulation insights. *J. Environ. Chem. Eng.* **2025**, *13*, 117536. [[CrossRef](#)]
43. Calzia, D.; Panfoli, I.; Ravera, S.; Dazzi, E.; Gandolfo, S.; Pepe, I.M.; Vergani, L.; Morelli, A.M. Structural modification of proteins by direct electric current from low voltage. *J. Biochem. Mol. Toxicol.* **2009**, *23*, 309–317. [[CrossRef](#)]

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.