

LETTER

Open Access



Improved recovery of NO₂ sensors using heterojunctions between transition metal dichalcogenides and ZnO nanoparticles

Leilei Wang¹ and Jungwook Choi^{1*} 

Abstract

The stable recovery of gas sensors is an important indicator for evaluating their performance. Hitherto, the use of external light sources and/or an increase in the operating temperature has been effective in improving the recovery rate of gas sensors. Herein, heterojunctions were formed between the two-dimensional transition metal dichalcogenide nanosheets and zero-dimensional ZnO nanoparticles to improve the recovery rate of a NO₂ sensor. Scanning electron microscopy and Raman spectroscopy suggested a successful deposition of ZnO nanoparticles onto the MoS₂ and WSe₂ nanosheets. The sensing response to 10 ppm NO₂ gas at 100 °C indicated that the heterojunction formed by ZnO and MoS₂ or WSe₂ successfully improved the recovery rate of the sensor by 11.87% and 19.44%, respectively, whereas the sensitivity remained constant. The proposed approach contributes to improving the performance of gas sensors.

Keywords Heterojunction, Molybdenum disulfide, Tungsten diselenide, Gas sensing, Recovery

Introduction

Nitrogen dioxide (NO₂) is considered a major pollutant affecting the environment and human health [1, 2]. In the past few decades, nanomaterials, such as metal oxides [3–5], transition metal dichalcogenides (TMDC) [6–8], and carbon-based materials [9–12], have been used as sensing layers of the chemiresistors to detect NO₂ gas. An ideal gas sensor should exhibit high sensitivity, fast response, full recovery, and a low detection limit.

Carbon-based materials, such as graphene and carbon nanotubes (CNT), have been widely studied owing to their excellent electrical conductivity, stability, high surface-to-volume ratios, and low toxicity [13–15]. Carbon-based NO₂ gas sensors exhibit excellent responses to ppb-level NO₂ at room temperature. However, these

sensors often require prolonged recovery times because of the strong bonding between NO₂ molecules and the sp²-carbon in carbon-based materials [16, 17], which significantly affects the overall performance of the carbon-based gas sensors.

On the other hand, metal oxide-based NO₂ gas sensors, such as ZnO, TiO₂, WO₃, In₂O₃, and SnO₂, offer several advantages, including rapid response, high sensitivity, simplicity, and easy synthesis [18–23]. In particular, ZnO has garnered significant attention owing to its stable chemical and physical properties, simple synthesis, cost-effectiveness, and nontoxicity. ZnO has been widely employed in the fabrication of gas sensors in various forms, including nanowires [24], nanorods [25], and nanoflakes [26]. However, the ZnO-based gas sensors typically require operating temperatures higher than 200 °C [16, 27–29].

Gas sensors based on TMDC, such as MoS₂, WS₂, and WSe₂, can detect NO₂ and NH₃ gases at room temperature [30–34] owing to their distinctive layered structures, unique photoelectric and charge transfer properties, air

*Correspondence:

Jungwook Choi
choij@cau.ac.kr

¹ School of Mechanical Engineering, Chung-Ang University, Seoul 06974, Republic of Korea

stability, and presence of abundant active sites (e.g., sulfur vacancies and edge sites) [35–38]. However, low sensitivity, slow response, and poor recovery are the major limitations associated with TMDC-based NO_2 gas sensors [39–41].

Chemical doping [42], exposed edge positions [43], photoactivation [44], and noble metal/other nanomaterial functionalization [45–47] have been employed to enhance the sensitivity of sensors. Furthermore, recovery rate, which is one of the critical performance indicators for sensors, needs to be improved. Heterojunctions, external light assistance, and high operating temperatures have been reported to improve sensor recovery rate [15, 44, 48–50]. Among them, heterojunctions have received significant attention because of their energy-saving capabilities.

In this study, heterojunctions were fabricated to improve the recovery of TMDC-based gas sensors. The recovery rate of the sensors could be improved by approximately 5.72–11.87% and 8.10–19.44% via spray-coating of a small amount of n-type ZnO nanoparticles onto the p-type MoS_2 and WSe_2 nanosheets, respectively.

Results and discussion

The TMDC and diluted ZnO dispersions are successively spray-coated onto a SiO_2 wafer with an interdigitated Au electrode to form a heterojunction (Fig. 1). We employed tip sonication to exfoliate bulk TMDC, transforming

it into a few-layered structure to increase the surface area. Initially, 300 mg of bulk TMDC powder purchased from Alfa Aesar was placed into 100 ml of isopropyl alcohol (IPA) and subjected to tip sonication for 4 h at 150 W power. The TMDC-containing beaker remained immersed in an ice and water mixture throughout the exfoliation process. Subsequently, the exfoliated TMDC solution underwent centrifugation at 2000 rpm for 1 h, yielding a supernatant enriched with few-layered TMDC. The resulting concentrations of the MoS_2 and WSe_2 dispersions were 0.06 and 0.075 mg/ml, respectively. The ZnO solution purchased from Sigma Aldrich was diluted to 0.06 mg/ml. The TMDC/ZnO heterojunction was confined to the dimensions of 4.2 mm $\times$ 1.85 mm using a shadow mask and annealed at 250 $^\circ\text{C}$ for 2 h in an Ar atmosphere to remove impurities. The finally prepared TMDC/ZnO heterojunction sample is shown in Fig. 1c.

Figure 2a, c demonstrate the TMDC nanosheets exfoliated through ultrasonic treatment with sizes predominantly ranging from 100 to 300 nm. These nanosheets are uniformly dispersed on a SiO_2 wafer, forming a compact and conductive network. The interstitial spaces between the TMDC nanosheets facilitate the penetration of NO_2 gas molecules, thereby leading to an increased number of adsorption sites for NO_2 gas. Figure 2b, d demonstrate randomly distributed ZnO nanoparticles (30–80 nm) on the TMDC nanosheets (indicated by red arrows). The SEM images of undiluted ZnO nanoparticles are featured

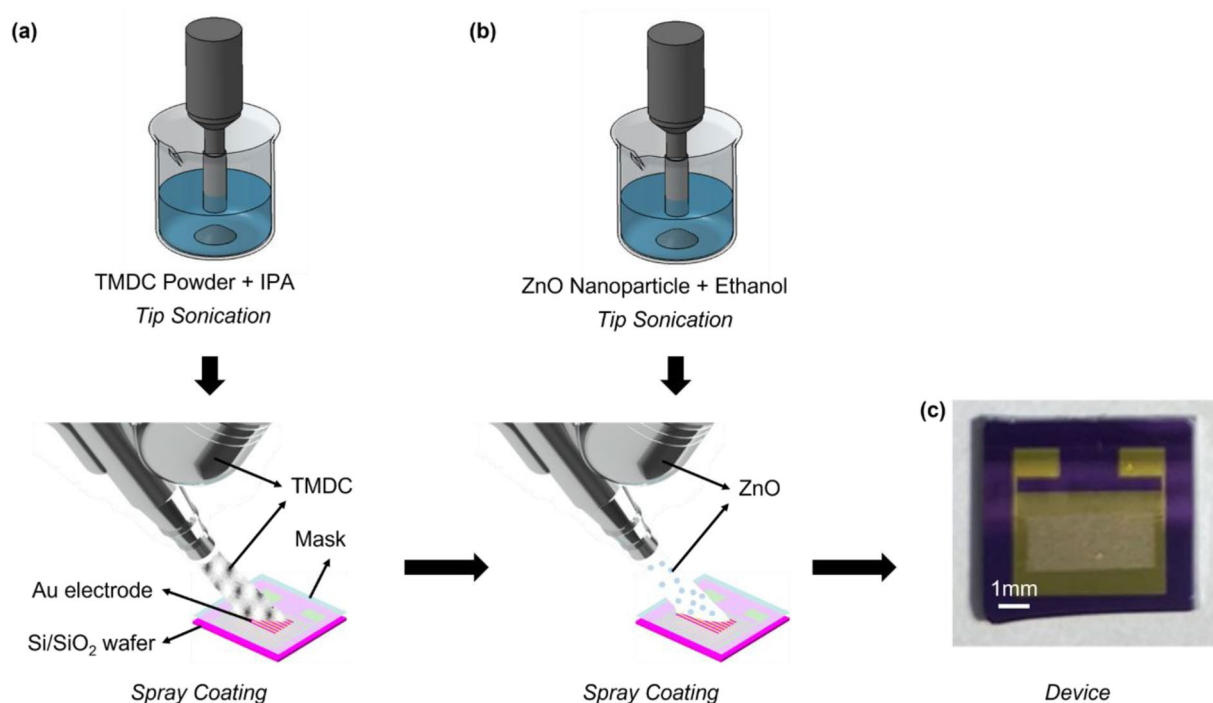


Fig. 1 Schematic of TMDC/ZnO-based NO_2 gas sensor fabrication process. (TMDC: transition metal dichalcogenides; IPA: Isopropylalcohol)

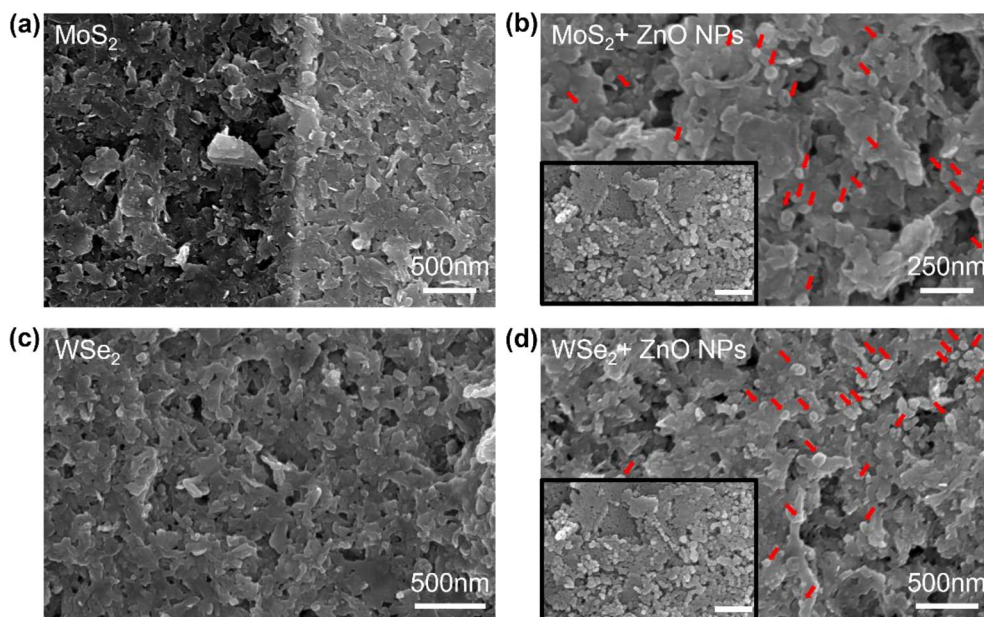


Fig. 2 Scanning electron microscopic images of **a** MoS₂, **b** MoS₂/ZnO-, **c** WSe₂-, **d** WSe₂/ZnO-based gas sensors. The red arrow represents the ZnO nanoparticles (NP). The insets in **b** and **d** show SEM image of undiluted ZnO nanoparticles. The scale bars in the insets are 250 nm

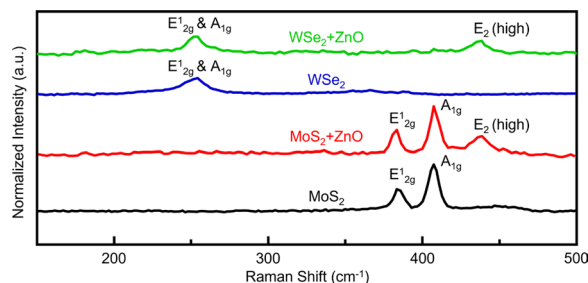


Fig. 3 Raman spectra of the transition metal dichalcogenides (TMDC)-based gas sensor (excited by 532 nm laser). Unlike TMDC, the TMDC/ZnO sensor exhibits the E₂ (high) characteristic peak of ZnO

in the inset of Fig. 2b, d. Aggregation of ZnO nanoparticles occurred due to its high concentration. On the other hand, we diluted and re-dispersed ZnO nanoparticles for sensor fabrication in order to minimize the aggregation of nanoparticles.

As shown in Fig. 3, the Raman spectrum of the TMDC-based gas sensor excited by a 532 nm laser exhibits prominent peaks of MoS₂ located at 407.41 and 383.4 cm⁻¹. These two peaks correspond to the out-of-plane (A_{1g}) and in-plane (E_{2g}) modes of MoS₂. The difference in the positions of these peaks is ~24.01 cm⁻¹, indicating the presence of a few-layered structure of the MoS₂ [51]. A single prominent Raman peak of WSe₂ appears at 254.3 cm⁻¹, which can be assigned to the overlapping of E_{2g} and A_{1g},

and indicates a few-layered structure of the WSe₂ [52]. Furthermore, the typical E₂ (high) peak of ZnO is observed at 438.2 cm⁻¹ in MoS₂/ZnO and WSe₂/ZnO spectra [53], indicating the successful deposition of ZnO nanoparticles onto the TMDC nanosheets.

In this work, we used a custom-built gas chamber for conducting gas sensing experiments. This chamber is seamlessly integrated with both a gas mass flow controller and a temperature controller. Throughout the experimentation process, temperature was precisely maintained as the sample stage within the gas chamber was consistently maintained at 100 °C. To facilitate the experiments, the regulated flow of NO₂ gas and custom dry air was introduced through a mass flow controller. This ensured a steady total flow rate of 500 sccm. The I–V curves and resistance measurements of the gas sensor were accurately recorded using a Keithley 2634B sourcemeter. The TMDC/ZnO-based sensor exhibits a significantly higher resistance than the TMDC-based sensor, which can be attributed to the formation of heterojunctions (Fig. 4a, b). Furthermore, the addition of ZnO nanoparticles significantly reduces the signal drift of the TMDC-based sensor, whereas the response of the sensor remains unchanged (Fig. 4c). We studied the recovery rate of the sensors which can be defined as [54, 55]:

$$\text{Recovery Rate} = \frac{(I - I_{10\text{min}})}{(I - I_0)} \times 100\%$$

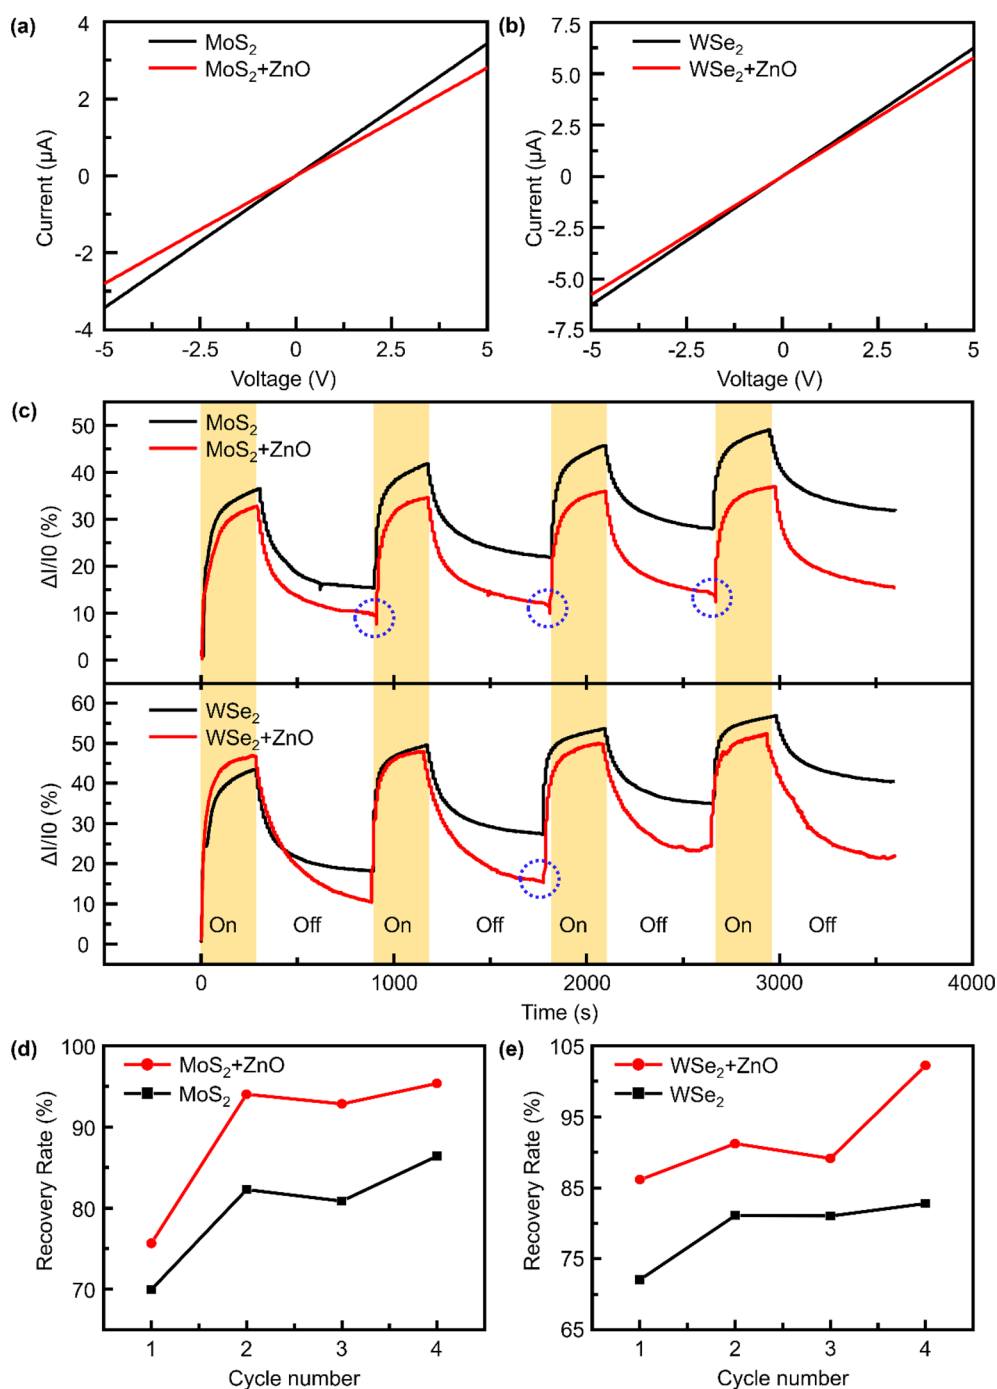


Fig. 4 I-V characteristics of **a** MoS₂, MoS₂/ZnO, **b** WSe₂ and WSe₂/ZnO-based gas sensor in air environment at 100 °C. **c** Gas sensing response of transition metal dichalcogenides (TMDC)-based gas sensor to 10 ppm NO₂ gas at 100 °C. The part where the conductivity decreased at the early stage of NO₂ exposure is outlined by the blue dotted line. **d** Recovery rate per cycle of MoS₂ and MoS₂/ZnO-based gas sensor. **e** Recovery rate per cycle of WSe₂ and WSe₂/ZnO-based gas sensor

while I_0 is the initial current of the sensor, I is the current generated by the sensor exposed to NO₂ gas, and I_{10min} is the current of the sensor after shutting off the NO₂ gas for 10 min. Compared with MoS₂ and WSe₂,

the recovery rates of MoS₂/ZnO and WSe₂/ZnO sensors improved by ~5.72–11.87% and ~8.10–19.44%, respectively (Fig. 4d, e). This is attributed to the variation in

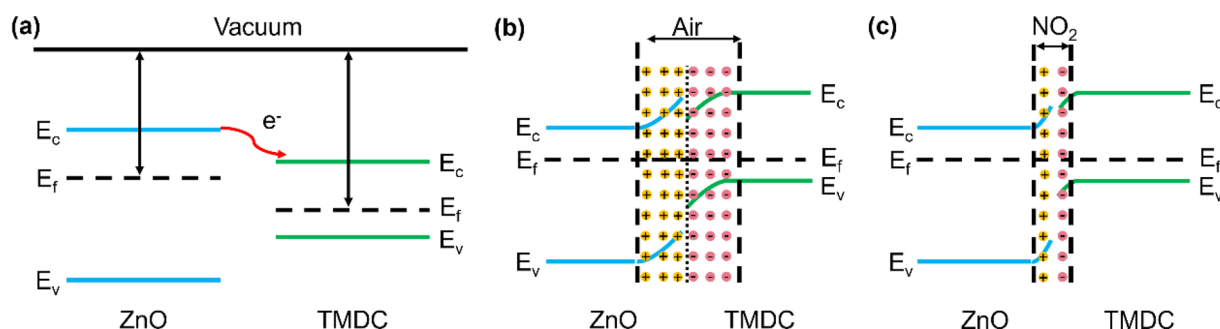


Fig. 5 Band diagrams of transition metal dichalcogenides (TMDC)/ZnO heterojunction **a** before equilibrium, **b** after equilibrium in air and **c** NO_2 gas atmosphere

the built-in field inside the heterojunction between the n-type ZnO and p-type TMDC.

The electrons of ZnO near the ZnO/TMDC interface tend to diffuse into TMDC, whereas the holes in TMDC tend to diffuse into ZnO before the Fermi levels of the p-type TMDC and n-type ZnO reach equilibrium (Fig. 5a). This leads to the formation of a depletion layer on the ZnO surface that gradually generates an internal electric field in the ZnO/TMDC interface region. The internal electric field hinders further diffusion of carriers (Fig. 5b). When the sensor is exposed to NO_2 gas, the NO_2 molecules first capture electrons from ZnO with large adsorption energy and increase the width of the built-in electric field, resulting in a decrease in the sensor conductivity at the initial stage of NO_2 gas influx (the parts inside the blue dotted line in Fig. 4c). As the influx of NO_2 gas continues, NO_2 molecules start capturing electrons from the p-type TMDC surface with many active sites. The balance of the built-in electric field is broken, the holes accumulated at the ZnO side return to TMDC, and the width of the built-in electric field decreases (Fig. 5c). Furthermore, the desorption of NO_2 molecules on ZnO with large adsorption energy is slow and incomplete when air is introduced. This significantly improves the recovery rate of TMDC/ZnO-based gas sensors. Nonetheless, incompletely desorbed NO_2 molecules are still present on TMDC. The recovery rate could be further improved by employing external light sources [56, 57].

Conclusion

In this study, heterojunctions were fabricated via spray-coating a small amount of n-type ZnO nanoparticles onto the p-type TMDC nanosheets. SEM images and Raman spectra confirmed the successful deposition of small ZnO nanoparticles onto the large TMDC nanosheets. Furthermore, the fabricated heterojunction successfully improved the recovery rate of MoS_2/ZnO and $\text{WSe}_2/$

ZnO sensors by $\sim 5.72\text{--}11.87\%$ and $\sim 8.10\text{--}19.44\%$, respectively. This study is expected to contribute to the development of high-performance NO_2 gas sensors.

Abbreviations

NO_2	Nitrogen dioxide
TMDC	Transition metal dichalcogenides
CNT	Carbon nanotube
SiO_2	Silicon dioxide

Acknowledgements

Not applicable.

Author contributions

LW: contributed to synthesis, analysis, writing of the manuscript. JC: contributed to, Conceptualization, validation, Writing-review and editing.

Funding

This research was supported by the Basic Science Research Program of the National Research Foundation of Korea (NRF), funded by the Ministry of Science, ICT, and Future Planning (2022R1A2C4001577).

Availability of data and materials

The datasets used and/or analyzed during the current study are available from the corresponding author on request.

Declarations

Competing interests

The authors declare that they have no competing interests.

Received: 21 July 2023 Accepted: 28 August 2023

Published online: 11 September 2023

References

- Bai M, Chen M, Li X, Wang Q (2022) One-step CVD growth of ZnO nanorod/ SnO_2 film heterojunction for NO_2 gas sensor. *Sens Actuators B* 373:132738
- Wang N, Tao W, Gong X, Zhao L, Wang T, Zhao L, Liu F, Liu X, Sun P, Lu G (2022) Highly sensitive and selective NO_2 gas sensor fabricated from Cu_2O -CuO microflowers. *Sens Actuators B* 362:131803
- Xiong Y, Lu W, Ding D, Zhu L, Li X, Ling C, Xue Q (2017) Enhanced room temperature oxygen sensing properties of LaOCl - SnO_2 hollow spheres by UV light illumination. *ACS Sens* 2:679–686

4. Patil VL, Vanalakara SA, Shendage SS, Patil SP, Kamble AS, Tarwal NL, Sharma KK, Kim JH, Patil PS (2019) Fabrication of nanogranular TiO₂ thin films by SILAR technique: application for NO₂ gas sensor. *Inorg Nano Metal Chem* 49:191–197
5. Navale YH, Navale ST, Stadler FJ, Ramgir NS, Patil VB (2019) Enhanced NO₂ sensing aptness of ZnO nanowire/CuO nanoparticle heterostructure-based gas sensors. *Ceram Int* 45:1513–1522
6. Lee WS, Choi J (2019) Hybrid integration of carbon nanotubes and transition metal dichalcogenides on cellulose paper for highly sensitive and extremely deformable chemical sensors. *ACS Appl Mater Interfaces* 11:19363–19371
7. Ko KY, Song J-G, Kim Y, Choi T, Shin S, Lee CW, Lee K, Koo J, Lee H, Kim J, Lee T, Park J, Kim H (2016) Improvement of gas-sensing performance of large-area tungsten disulfide nanosheets by surface functionalization. *ACS Nano* 10:9287–9296
8. Lee WS, Choi J (2019) Two-dimensional tungsten diselenides integrated on paper substrate for highly flexible and sensitive gas sensor. In: 2019 20th international conference solid-state sensors, actuators microsystems eurosensors XXXIII, TRANSDUCERS 2019 EUROSENSORS XXXIII, IEEE, Berlin, Germany, 23–27 June 2019
9. Sayago I, Santos H, Horrillo MC, Aleixandre M, Fernández MJ, Terrado E, Tacchini I, Aroz R, Maser WK, Benito AM, Martínez MT, Gutiérrez J, Muñoz E (2008) Carbon nanotube networks as gas sensors for NO₂ detection. *Talanta* 77:758–764
10. Kumar D, Chaturvedi P, Saho P, Jha P, Chouksey A, Lal M, Rawat JSBS, Tandon RP, Chaudhury PK (2017) Effect of single wall carbon nanotube networks on gas sensor response and detection limit. *Sens Actuators B* 240:1134–1140
11. Seekaew Y, Phokharatkul D, Wisitsoraat A, Wongchoosuk C (2017) Highly sensitive and selective room-temperature NO₂ gas sensor based on bilayer transferred chemical vapor deposited graphene. *Appl Surf Sci* 404:357–363
12. Pearce R, Iakimov T, Andersson M, Hultman L, Spetz AL, Yakimova R (2011) Epitaxially grown graphene based gas sensors for ultra sensitive NO₂ detection. *Sens Actuators B* 155:451–455
13. Alam MN, Kumar V, Lee D-J, Choi J (2023) Synergistically toughened silicone rubber nanocomposites using carbon nanotubes and molybdenum disulfide for stretchable strain sensors. *Compos Part B Eng* 259:110759
14. Wang L, Choi J (2022) Highly stretchable strain sensors with improved sensitivity enabled by a hybrid of carbon nanotube and graphene. *Micro Nano Syst Lett* 10:17
15. Lee SW, Lee W, Hong Y, Lee G, Yoon DS (2018) Recent advances in carbon material-based NO₂ gas sensors. *Sens Actuators B* 255:1788–1804
16. Hong HS, Phuong NH, Huong NT, Nam NH, Hue NT (2019) Highly sensitive and low detection limit of resistive NO₂ gas sensor based on a MoS₂/graphene two-dimensional heterostructures. *Appl Surf Sci* 492:449–454
17. Choi J, Kim J (2015) Defective carbon nanotube-silicon heterojunctions for photodetector and chemical sensor with improved responses. *J Micromech Microeng* 25:115004
18. Li Z, Li H, Wu Z, Wang M, Luo J, Torun H, Hu P, Yang C, Grundmann M, Liu X, Fu YQ (2019) Advances in designs and mechanisms of semiconducting metal oxide nanostructures for high-precision gas sensors operated at room temperature. *Mater Horiz* 6:470–506
19. Zhang Z, Haq M, Wen Z, Ye Z, Zhu L (2018) Ultrasensitive ppb-level NO₂ gas sensor based on WO₃ hollow nanospheres doped with Fe. *Appl Surf Sci* 434:891–897
20. Zhou P, Shen Y, Lu W, Zhao S, Li T, Zhong X, Cui B, Wei D, Zhang Y (2020) Highly selective NO₂ chemiresistive gas sensor based on hierarchical In₂O₃ microflowers grown on clinoptilolite substrates. *J Alloys Compd* 828:154395
21. Bhati VS, Ranwa S, Fanetti M, Valant M, Kumar M (2018) Efficient hydrogen sensor based on Ni-doped ZnO nanostructures by RF sputtering. *Sens Actuators B* 255:588–597
22. Wang J, Shen Y, Li X, Xia Y, Yang C (2019) Synergistic effects of UV activation and surface oxygen vacancies on the room-temperature NO₂ gas sensing performance of ZnO nanowires. *Sens Actuators B* 298:126858
23. Lu W-C, Kumar SS, Chen Y-C, Hsu C-M, Lin H-N (2019) Au/Cu₂O/ZnO ternary nanocomposite for low concentration NO₂ gas sensing at room temperature. *Mater Lett* 256:126657
24. Öztürk S, Kiliç N, Taştaltın N, Öztürk ZZ (2011) A comparative study on the NO₂ gas sensing properties of ZnO thin films, nanowires and nanorods. *Thin Solid Films* 520:932–938
25. Chang C-J, Lin C-Y, Chen J-K, Hsu M-H (2014) Ce-doped ZnO nanorods based low operation temperature NO₂ gas sensors. *Ceram Int* 40:10867–10875
26. Kaneti YV, Yue J, Jiang X, Yu A (2013) Controllable synthesis of ZnO nanoflakes with exposed (10⁻¹⁰) for enhanced gas sensing performance. *J Phys Chem C* 117:13153–13162
27. Zhao S, Wang G, Liao J, Lv S, Zhu Z, Li Z (2018) Vertically aligned MoS₂/ZnO nanowires nanostructures with highly enhanced NO₂ sensing activities. *Appl Surf Sci* 456:808–816
28. Tamvakos A, Korir K, Tamvakos D, Calestani D, Cicero G, Pullini D (2016) NO₂ gas sensing mechanism of ZnO thin-film transducers: Physical experiment and theoretical correlation study. *ACS Sens* 1:406–412
29. Lee K, Baek D-H, Na H, Choi J, Kim J (2018) Simple fabrication method of silicon/tungsten oxide nanowires heterojunction for NO₂ gas sensors. *Sens Actuators B* 265:522–528
30. Lee E, Yoon YS, Kim D-J (2018) Two-dimensional transition metal dichalcogenides and metal oxide hybrids for gas sensing. *ACS Sens* 3:2045–2060
31. Agrawal AV, Kumar N, Kumar M (2021) Strategy and future prospects to develop room-temperature-recoverable NO₂ gas sensor based on two-dimensional molybdenum disulfide. *Nano Micro Lett* 13:38
32. Goswami P, Gupta G (2022) Recent progress of flexible NO₂ and NH₃ gas sensors based on transition metal dichalcogenides for room temperature sensing. *Mater Today Chem* 23:100726
33. Guo R, Han Y, Su C, Chen X, Zeng M, Hu N, Su Y, Zhou Z, Wei H, Yang Z (2019) Ultrasensitive room temperature NO₂ sensors based on liquid phase exfoliated WSe₂ nanosheets. *Sens Actuators B* 300:127013
34. Sharma I, Kumar KN, Choi J (2023) Highly sensitive chemiresistive detection of NH₃ by formation of WS₂ nanosheets and SnO₂ quantum dot heterostructures. *Sens Actuators B* 375:132899
35. Han Y, Huang D, Ma Y, He G, Hu J, Zhang J, Hu N, Su Y, Zhou Z, Zhang Y, Yang Z (2018) Design of hetero-nanostructures on MoS₂ nanosheets to boost NO₂ room-temperature sensing. *ACS Appl Mater Interfaces* 10:22640–22649
36. Kumar RR, Murugesan T, Dash A, Hsu C-H, Gupta S, Manikandan A, Anbalagan A, Lee C-H, Tai N-H, Chueh Y-L, Lin H-N (2021) Ultrasensitive and light-activated NO₂ gas sensor based on networked MoS₂/ZnO nanohybrid with adsorption/desorption kinetics study. *Appl Surf Sci* 536:147933
37. Choi J, Zhang H, Choi JH (2016) Modulating optoelectronic properties of two-dimensional transition metal dichalcogenide semiconductors by photoinduced charge transfer. *ACS Nano* 10:1671–1680
38. Choi J, Zhang H, Du H, Choi JH (2016) Understanding solvent effects on the properties of two-dimensional transition metal dichalcogenides. *ACS Appl Mater Interfaces* 8:8864–8869
39. Li H, Yin Z, He Q, Li H, Huang X, Lu G, Fam DWH, Tok AIY, Zhang Q, Zhang H (2012) Fabrication of single- and multilayer MoS₂ film-based field-effect transistors for sensing NO at room temperature. *Small* 8:63–67
40. Lee K, Gatensby R, McEvoy N, Hallam T, Duesberg GS (2013) High-performance sensors based on molybdenum disulfide thin films. *Adv Mater* 25:6699–6702
41. Li H, Wu J, Yin Z, Zhang H (2014) Preparation and applications of mechanically exfoliated single-layer and multilayer MoS₂ and WSe₂ nanosheets. *Acc Chem Res* 47:1067–1075
42. Zhang D, Wu J, Li P, Cao Y (2017) Room-temperature SO₂ gas-sensing properties based on a metal-doped MoS₂ nanoflower: an experimental and density functional theory investigation. *J Mater Chem A* 5:20666–20677
43. Cho S-Y, Kim SJ, Lee Y, Kim J-S, Jung W-B, Yoo H-W, Kim J, Jung H-T (2015) Highly enhanced gas adsorption properties in vertically aligned MoS₂ layers. *ACS Nano* 9:9314–9321
44. Late DJ, Huang Y-K, Liu B, Acharya J, Shirodkar SN, Luo J, Yan A, Charles D, Waghmare UV, David VP, Rao CNR (2013) Sensing behavior of atomically thin-layered MoS₂ transistors. *ACS Nano* 7:4879–4891
45. Cho S-Y, Koh H-J, Yoo H-W, Kim J-S, Jung H-T (2017) Tunable volatile-organic-compound sensor by using Au nanoparticle incorporation on MoS₂. *ACS Sens* 2:183–189
46. Long H, Harley-Trochimczyk A, Pham T, Tang Z, Shi T, Zettl A, Carraro C, Worsley MA, Maboudian R (2016) High surface area MoS₂/graphene

- hybrid aerogel for ultrasensitive NO₂ detection. *Adv Funct Mater* 26:5158–5165
47. Cui S, Wen Z, Huang X, Chang J, Chen J (2015) Stabilizing MoS₂ nanosheets through SnO₂ nanocrystal decoration for high-performance gas sensing in air. *Small* 11:2305–2313
 48. Shim Y-S, Kwon KC, Suh JM, Choi KS, Song YG, Sohn W, Choi S, Hong K, Jeon J-M, Hong S-P, Kim S, Kim SY, Kang C-Y, Jang HW (2018) Synthesis of numerous edge sites in MoS₂ via SiO₂ nanorods platform for highly sensitive gas sensor. *ACS Appl Mater Interfaces* 10:31594–31602
 49. Liu C, Chen X, Luo H, Li B, Shi J, Fan C, Yang J, Zeng M, Zhou Z, Hu N, Su Y, Yang Z (2021) Highly sensitive and recoverable room-temperature NO₂ gas detection realized by 2D/0D MoS₂/ZnS heterostructures with synergistic effects. *Sens Actuators B* 347:130608
 50. Jaiswal J, Sanger A, Tiwari P, Chandra R (2020) MoS₂ hybrid heterostructure thin film decorated with CdTe quantum dots for room temperature NO₂ gas sensor. *Sens Actuators B* 305:127437
 51. Castellanos-Gomez A, van der Zant HSJ, Steele GA (2014) Folded MoS₂ layers with reduced interlayer coupling. *Nano Res* 7:572–578
 52. Sahin H, Tongay S, Horzum S, Fan W, Zhou J, Li J, Wu J, Peeters FM (2013) Anomalous Raman spectra and thickness-dependent electronic properties of WSe₂. *Phys Rev B* 87:165409
 53. Liu C, Qiu Y, Wang F, Wang K, Liang Q, Chen Z (2017) Design of core-shell structured ZnO/ZnS hybridized with graphite-like C₃N₄ for highly efficient photoelectrochemical water splitting. *Adv Mater Interfaces* 4:1700681
 54. Feng Z, Xie Y, Chen J, Yu Y, Zheng S, Zhang R, Li Q, Chen X, Sun C, Zhang H, Pang W, Liu J, Zhang D (2017) Highly sensitive MoTe₂ chemical sensor with fast recovery rate through gate biasing. *2D Mater* 4:025018
 55. Yang Z, Jiang L, Wang J, Liu F, He J, Liu A, Lv S, You R, Yan X, Sun P, Wang C, Duan Y, Lu G (2021) Flexible resistive NO₂ gas sensor of three-dimensional crumpled MXene Ti₃C₂T_x/ZnO spheres for room temperature application. *Sens Actuators B* 326:128828
 56. Kang Y, Pyo S, Jo E, Kim J (2019) Light-assisted recovery of reacted MoS₂ for reversible NO₂ sensing at room temperature. *Nanotechnology* 30:355504
 57. Tabata H, Matsuyama H, Goto T, Kubo O, Katayama M (2021) Visible-light-activated response originating from carrier mobility modulation of NO₂ gas sensors based on MoS₂ monolayers. *ACS Nano* 15:2542–2553

Publisher's Note

Springer Nature remains neutral with regard to jurisdictional claims in published maps and institutional affiliations.

Submit your manuscript to a SpringerOpen[®] journal and benefit from:

- Convenient online submission
- Rigorous peer review
- Open access: articles freely available online
- High visibility within the field
- Retaining the copyright to your article

Submit your next manuscript at ► [springeropen.com](https://www.springeropen.com)